

# Tunable Charge Detectors for Semiconductor Quantum Circuits

**C. Rössler**

Solid State Physics Laboratory, ETH Zurich, 8093 Zurich, Switzerland

E-mail: roessler@phys.ethz.ch

**T. Krähenmann**

Solid State Physics Laboratory, ETH Zurich, 8093 Zurich, Switzerland

**S. Baer**

Solid State Physics Laboratory, ETH Zurich, 8093 Zurich, Switzerland

**T. Ihn**

Solid State Physics Laboratory, ETH Zurich, 8093 Zurich, Switzerland

**K. Ensslin**

Solid State Physics Laboratory, ETH Zurich, 8093 Zurich, Switzerland

**C. Reichl**

Solid State Physics Laboratory, ETH Zurich, 8093 Zurich, Switzerland

**W. Wegscheider**

Solid State Physics Laboratory, ETH Zurich, 8093 Zurich, Switzerland

**Abstract.** Nanostructures defined in high-mobility two-dimensional electron systems offer a unique way of controlling the microscopic details of the investigated device. Quantum point contacts play a key role in these investigations, since they are not only a research topic themselves, but turn out to serve as convenient and powerful detectors for their electrostatic environment. We investigate how the sensitivity of charge detectors can be further improved by reducing screening, increasing the capacitive coupling between charge and detector and by tuning the quantum point contacts' confinement potential into the shape of a localized state. We demonstrate the benefits of utilizing a localized state by performing fast and well-resolved charge detection of a large quantum dot in the quantum Hall regime.

PACS numbers: 72.20.-i, 73.21.-b, 73.23.-b, 73.63.-b, 75.75.-c

## 1. Introduction


Clean low-dimensional electron systems exhibit a rich spectrum of interaction-induced effects like the formation of composite fermions [1, 2], the  $\nu = 5/2$  state [3], the 0.7 anomaly [4, 5, 6] or the Kondo effect [7, 8], which are subject of current fundamental research. By confining interaction-induced states via quantum point contacts (QPCs) [9, 10], interferometers or quantum dots (QDs) [11, 12], one hopes to utilize experimental techniques like coherent charge- and spin-manipulation [13, 14], full counting statistics [15] or controllable coupling to other two-level systems [16, 17] to gain further insight into the underlying physics. Many of these experiments rely on detecting changes of a localized charge state via an adjacent QPC serving as the charge detector [18, 19, 20]. Its detection fidelity poses a fundamental limit to the readout speed of qubits and has therefore been subject of several investigations. It was found that the detection fidelity can be improved by maximizing both the detector's pinch-off slope and the capacitance between QD and QPC [21]. The detector slope was increased by employing SETs [22, 23, 24] or QDs [25] as detectors. The capacitive coupling can be improved by placing QD and detector in close proximity to each other [26, 27], by avoiding metal gates in between QD and detector [28] and/or by employing a floating gate on top of QD and detector.

Unfortunately, efficient charge detection is difficult to accomplish in  $\text{Al}_x\text{Ga}_{1-x}\text{As}$ -based ultra-high-mobility two-dimensional electron systems (2DESs) due to the methods employed for achieving the high mobilities.

- (i) Screening layers between 2DES and doping layer were found to suppress remote ionized impurity scattering [29, 30] but it comes at the cost of hysteresis effects and temporal drifts when investigating electrostatically defined structures [9, 10, 31]. Moreover, transport experiments on QPCs defined in high-mobility 2DESs suggest increased screening of the confinement potential due to the presence of screening layers [32] which might further reduce the capacitive coupling between QD and detector.
- (ii) High-mobility 2DESs are usually defined deeper underneath the surface ( $\gtrsim 200$  nm) compared to standard 2DESs ( $\lesssim 100$  nm). The increased distance to metal gates reduces screening, but being farther away from the surface reduces the coupling between QD and detector due to the higher dielectric constant of GaAs compared to vacuum. Moreover, since the typical distance between QD and detector scales with the distance between 2DES and surface gates, the coupling is expected to decrease further.
- (iii) Many experiments on high-mobility 2DESs aim at confining (fractional) quantum Hall states. If the sample is investigated in the quantum Hall regime, the Hall resistance is added to the detector circuit's impedance. Hence, a given change of the detector's transmission results in a smaller absolute change of the detector current.

## 2. Charge Detection Experiments


We present a study of several charge detectors realized in high-mobility 2DESs. The 2DES is defined at a GaAs/Al<sub>x</sub>Ga<sub>1-x</sub>As heterointerface,  $z = 120$  nm (Samples 1, 2, 3) or  $z = 320$  nm (Sample 4) beneath the surface. The doping is realized in a region with reduced aluminium content  $x = 0.24$ , providing high mobilities without using additional screening layers [33]. Typical electron sheet densities and mobilities without LED-illumination are ( $n_S = 1.4 \times 10^{11} \text{ cm}^{-2}$ ,  $\mu = 9 \times 10^6 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$ , Samples 1, 2, 3) and ( $n_S = 1.3 \times 10^{11} \text{ cm}^{-2}$ ,  $\mu = 10 \times 10^6 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$ , Sample 4). After performing optical lithography to define mesa, Ohmic contacts and gate leads, the inner part of the structure is defined by electron beam lithography and subsequent deposition of Ti/Au gates as shown in the scanning electron micrograph of Sample 1 in figure 1a). Applying negative voltages to the gates (bright areas) depletes the 2DES underneath and defines two QDs and two detectors. In order to compare the same geometry under different screening conditions, the barrier gate separating the right detector from the right QD is split which should reduce screening between QD and detector. Figure 1b) shows the differential conductance  $G_{\text{QDL}} = dI_{\text{QDL}}/dV_{\text{QDL-SD}}$  (measured at  $V_{\text{SD}} \approx 0$  V,  $T_{\text{el}} \approx 50$  mK) of the left QD (lower trace) as a function of the voltage applied to the QD plunger gate. Characteristic Coulomb blockade oscillations indicate the formation of a QD. The differential conductance of the detector is measured simultaneously and displays a step of  $\Delta G_{\text{DetL}} \sim 0.0015 \times 2e^2/h$  every time the charge on the QD changes by one electron. The magnitude of the step is a measure for the readout fidelity and was optimized by measuring the step height at different detector conductances. It was found that the readout step height is approximately constant for  $0.01 \times 2e^2/h \lesssim G_{\text{Det}} \lesssim 0.5 \times 2e^2/h$ . A likely explanation for this observation would be the compensation between two effects: the steeper detector-slope at  $G = 0.5 \times 2e^2/h$  versus reduced screening by the 2DES at lower conductance due to a reduced electron density in the vicinity of the detector. Since a lower detector current also results in less back-action from the measurement circuit on the QD [34, 35, 36, 37], the detectors are set to a conductance of  $G_{\text{Det}} \sim 0.1 \times 2e^2/h$ . The experiment is repeated with the right QD and a gapped detector and yields again Coulomb blockade oscillations (lower trace) and detector kinks (upper trace). This time the detector sensitivity is  $\Delta G_{\text{DetR}} \sim 0.007 \times 2e^2/h$ . Comparing our detector sensitivities to the best reported values for top-gate defined single QDs  $\Delta G \sim 0.004...0.006 \times 2e^2/h$  [18, 20, 38, 39], the left detector's performance appears to be below average, whereas the right detector is rather sensitive. We attribute the increased sensitivity of the right detector to the presence of the gap which should reduce both electrostatic screening and the lateral distance between QD and detector. Moreover, the gap can define a localized state which will be discussed later.

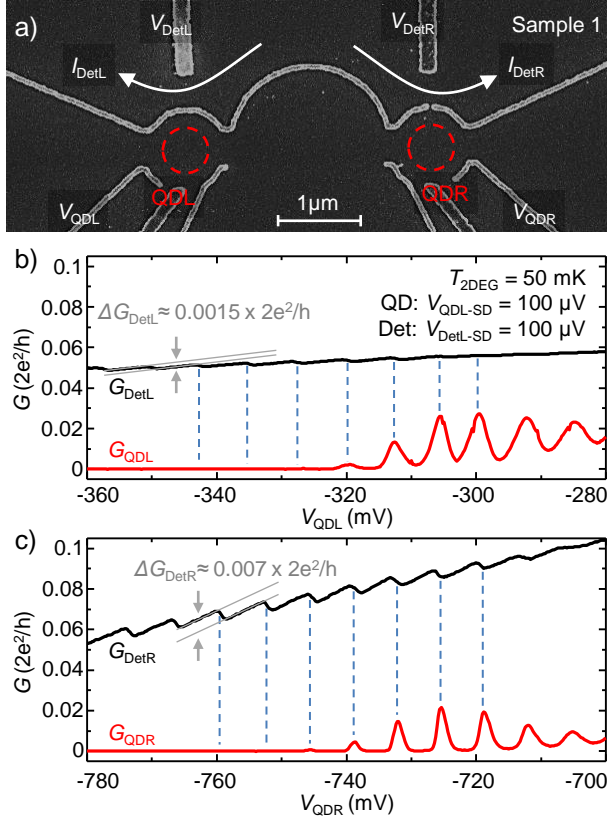

**Figure 1.** (color online) a) Scanning electron micrograph of Sample 1. Schottky gates appear bright, the crystal surface appears dark. Applying negative voltages to gates depletes the underlying electron gas and defines two QDs (dashed circles) and two constrictions serving as charge detectors (white arrows). The left and right half of the structure are identical with the exception of a gap in the gates between the right QD and its detector. b) Gate voltage  $V_{\text{QDL}}$  controls the number of electrons in the left QD, giving rise to Coulomb blockade oscillations in the differential conductance  $G_{\text{QDL}} = dI_{\text{QDL}}/dV_{\text{QDL-SD}}$  (red). Each change of the electron occupation number is accompanied by a kink in the differential conductance of the detector  $G_{\text{DetL}} = dI_{\text{DetL}}/dV_{\text{DetL-SD}}$  by typically  $\Delta G_{\text{DetL}} \sim 0.0015 \times 2e^2/h$  (black trace). c) Differential conductance of the right QD  $G_{\text{QDR}}$  and the right detector  $G_{\text{DetR}}$ , plotted as a function of gate voltage  $V_{\text{QDR}}$ . The high detector sensitivity of  $\Delta G_{\text{DetR}} \sim 0.007 \times 2e^2/h$  is attributed to the particular geometry of the detector gates, as will be shown later.


### 2.1. Increased coupling via floating gate

Further improvement of the detector sensitivity is expected by increasing the capacitive coupling between QD and detector via a floating gate. In the past, floating gates have been used between adjacent QDs [40, 41, 42] and were found to increase the capacitive coupling between them. Figure 2a) shows an image of Sample 2 which consists of QD, detector and a floating gate on top of them. A typical charge readout signal is shown in figure 2b) as a function of the QD's plunger gate voltage. The detector sensitivity is now  $\Delta G_{\text{Det}} \sim 0.02 \times 2e^2/h$ , roughly a factor of three better than literature values. However, in Sample 2 and two other similar samples (data not shown), severe charge rearrangements

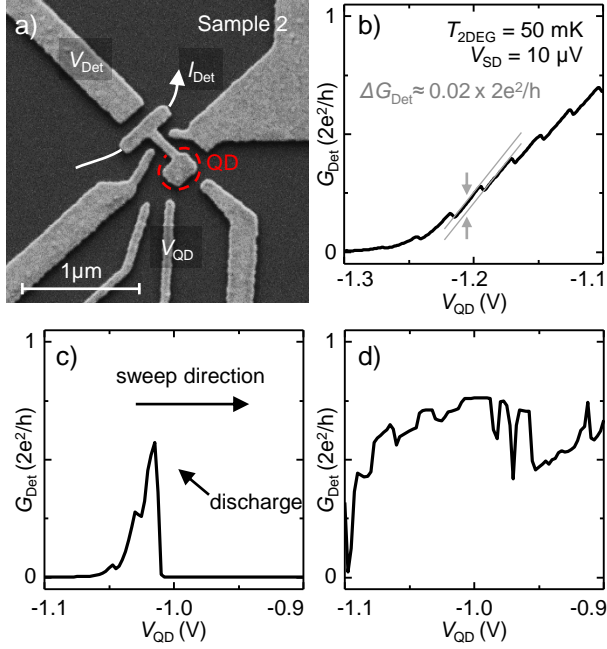

**Figure 2.** (color online) a) Scanning electron micrograph of Sample 2. A floating gate on top of both the QD and the detector is employed to increase capacitive coupling between the two. b) Detector conductance as a function of gate-voltage  $V_{\text{QD}}$ . Regular steps with  $\Delta G_{\text{Det}} \sim 0.02 \times 2e^2/h$  indicate charging of the QD measured by the detector. c) While repeatedly sweeping  $V_{\text{QD}}$ , a sudden change of the detector's conductance is observed (black arrow). The implied presence of additional negative charge in the vicinity of QD and detector is probably caused by charging of the floating gate. d) After the discharge, the conductance of the detector fluctuates while sweeping  $V_{\text{QD}}$ .


were observed within the first few days of the experiment. One example is shown in figure 2c). While measuring  $G_{\text{Det}}$  as a function of plunger gate voltage, a sudden decrease of  $G_{\text{Det}}$  is observed, corresponding to additional negative charge in the vicinity of the detector. The most likely explanation for such behavior is charging of the floating gate either due to electrons tunneling laterally from a neighboring gate, or vertically from the 2DES. In both cases, charging can hardly be avoided because whenever negative gate voltages are applied to gates on one side of the floating gate, a positive potential is induced on the other side of the floating gate and the Schottky barrier between the metal and GaAs is reduced. After charging,  $G_{\text{Det}}$  is fluctuating at a timescale of seconds, as can be seen from the gate-sweep shown in figure 2d). Random switching events indicate time- and/or voltage-dependent charge rearrangements between the floating gate and its environment. These results indicate that despite improving the charge readout sensitivity, our floating gates are difficult to handle because the necessarily strong lateral electric fields induce charging events.

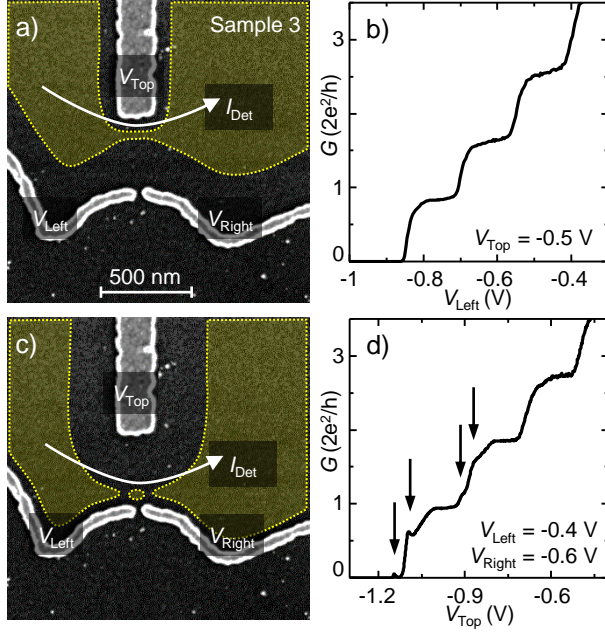

**Figure 3.** (color online) a) Scanning electron micrograph of Sample 3. Applying more negative voltages to the bottom gates shifts the conducting channel (sketched yellow area) upwards. b) Linear conductance of the channel, plotted as a function of  $V_{\text{Left}}$  while  $V_{\text{Right}} = V_{\text{Left}} - 0.2$  V. After subtracting a serial resistance of  $R_S = 10$  k $\Omega$  to account for cables, contacts and 2DES leads, the expected conductance quantization is observed. c) Applying more negative voltage to the top gate shifts the channel downwards, enabling a localization to form at the gap between the left and right gate. d) Linear conductance as a function of  $V_{\text{Top}}$ . Multiple charging events of a localized state are observed (arrows).

## 2.2. Inducing a localized state in the detector

Since the capacitive coupling can not easily be increased beyond using thin gates and introducing a gap in the barrier, we now focus on increasing the slope of the detector's pinch-off curve. Charge detection experiments on double QDs were previously performed using the Coulomb resonance of a third QD as detector [25]. Its slope depends on tunnel coupling and temperature and is much larger than values achievable with a typical saddle-point shaped constriction [43]. Shaping the electrostatic confinement potential of the detector is performed on Sample 3, which is lithographically identical to the right QD of Sample 1. Figure 3a) shows one top gate and two bottom gates which are used to tune the detector's confinement potential. Keeping  $V_{\text{Top}}$  at a moderate voltage and sweeping the voltage applied to the bottom gates should result in an single constriction as sketched by the shaded region (yellow). The linear conductance of the constriction is plotted in figure 3b) as a function of the voltage applied to the bottom gates and displays the expected quantization in multiples of  $2e^2/h$ . Figure 3c) illustrates the idea of pushing the detector closer to the gap between left and right gate. If the geometry and voltages are suitably chosen, it is possible to create a localized state. Figure 3d) shows the detector conductance as a function of  $V_{\text{Top}}$  while  $V_{\text{Left}}$  and  $V_{\text{Right}}$  are held constant. In contrast

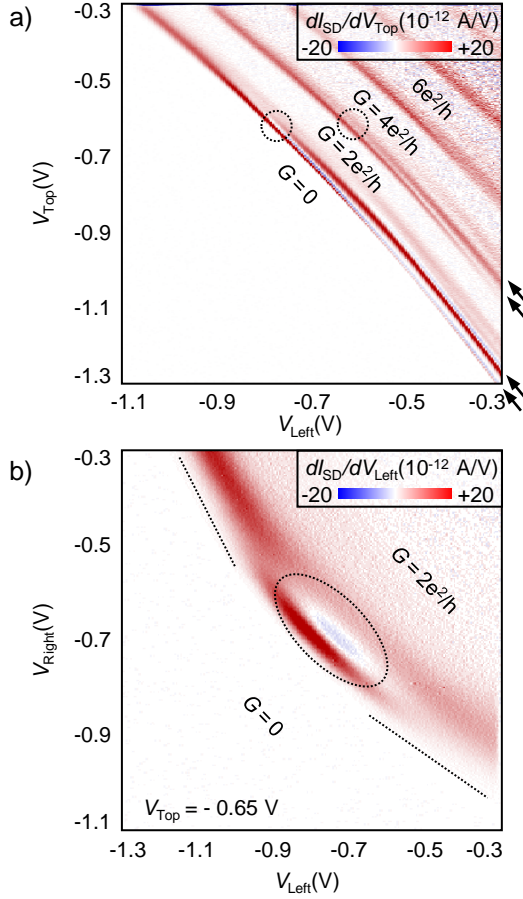

**Figure 4.** (color online) a) Transconductance  $G_T = dI/dV_{Top}$  plotted in color scale as a function of  $V_{Top}$  and  $V_{Left}$  with  $V_{Right} = V_{Left} - 0.2 \text{ V}$ . The conductance within white areas is constant and reaches from zero (bottom left) to conductance values of  $G = 1, 2, 3 \times 2e^2/h$ . Additional dark lines (indicated by arrows) emerge when the channel is shifted downwards, closer to the bottom gates. Dashed circles mark the positions where the localization starts to be formed. The resonances' positions relative to the conductance plateaus remain unchanged, implying the localized state shifts together with the channel (rather than being fixed in space). b) Changing the ratio of the left and right tunnel barriers at constant  $V_{Top} = -0.65 \text{ V}$ . Two dashed lines indicate where the channel is pinched off between the right and top gate (bottom-right of graph) and between left and top gate (top-left of graph). When both tunnel barriers are defined, the localized state emerges (dashed ellipse).

to the smooth conductance quantization observed earlier, the pinch-off curve exhibits several resonances (marked by arrows) indicating charging events of the localized state. In order to investigate the transition of the detector from QPC-like to QD-like, the full parameter sweep is shown in figure 4a). The transconductance  $G_T = dI/dV_{Top}$  is plotted in color scale (areas of constant conductance  $G = 0, 1, 2, 3 \times 2e^2/h$  appear white) as a function of  $V_{Left\&Right}$  and  $V_{Top}$ . Varying the ratio of  $V_{Left\&Right}$  and  $V_{Top}$  shifts the detector up ( $V_{Top} = -0.3 \text{ V}$ ) or down ( $V_{Top} = -1.3 \text{ V}$ ) as verified via scanning gate microscopy experiments [44]. While the pinch-off curve is smooth when the detector

is defined close to the top-gate, additional resonances appear in the middle of the plot (dashed circles) and become more pronounced as the detector is shifted towards the bottom gates. The resonances are parallel to each other, indicating that they have the same capacitance with respect to the gates and must therefore be multiple charging events of a single localized state. Moreover, the resonances are linked to the quantized plateaus. These observations indicate that in contrast to resonant scattering at an impurity [45], our localized state is not fixed in space but moves together with the detector channel. It is also noteworthy that the 0.7 anomaly is observed throughout the plot. It starts as a smeared area of finite slope around  $G \sim 0.7 \times 2e^2/h$  (top left) and turns into a pronounced plateau with conductance  $G \sim 0.6 \times 2e^2/h$  when the localized state is formed. Finite-bias data (not shown) also indicate the coexistence of the charged localized state with the characteristic half-plateaus of the 0.7 anomaly. For future studies, it might prove interesting to investigate this peculiar transition from an open QPC to a localized state as it might shed light on the microscopic nature of the 0.7 anomaly [6, 46, 47]. However, this topic is not further pursued in this paper.


In addition to moving the localization up/down, as a further test it can be moved left/right by varying the ratio of  $V_{\text{Left}}$  and  $V_{\text{Right}}$  at constant  $V_{\text{Top}}$ . The resulting plot of the transconductance  $G_T = dI/dV_{\text{Right}}$  is shown in figure 4b). Two dashed lines mark the pinch off between left and top gate (top-left of graph) and between right and top gate (bottom-right of graph). Only when both tunnel barriers are equally close to pinch-off, the localized state is formed (dashed ellipse). The resonances' slope of approximately  $45^\circ$  means that the localized state has about the same capacitance and hence distance to the left and right gate.

The estimates for the distances between localized state and the three gates strongly suggest that the presented geometry can be used to tune a QPC-like detector into a localized state that could be employed as a very sensitive charge detector. Defect-induced localized states were used to increase the sensitivity in other charge detection experiments, for example in graphene- and indium-arsenide-based devices [48, 26]. In contrast, our method applied with the low defect density of high-mobility heterostructures provides control of the position and coupling of the localized state.

### 2.3. Tuned charge detector in the quantum Hall regime

The technique of forming a localized state in a QPC was found to work in different geometries and heterostructures. Figure 5a) shows Sample 4, where experimental results had to be obtained under relatively difficult experimental conditions: a large QD, rather far away from the detector and defined in the quantum Hall regime. Five gates define QD (red circle) and detector (yellow area), another distant gate is used as QD plunger gate. Since the 2DES of Sample 4 is defined 320 nm beneath the surface, the lateral distances are scaled up compared to the previous samples. A magnetic field of  $B_\perp = 2.8 \text{ T}$  is applied perpendicular to the 2DES, corresponding to quantum Hall filling factor  $\nu = 2$ .



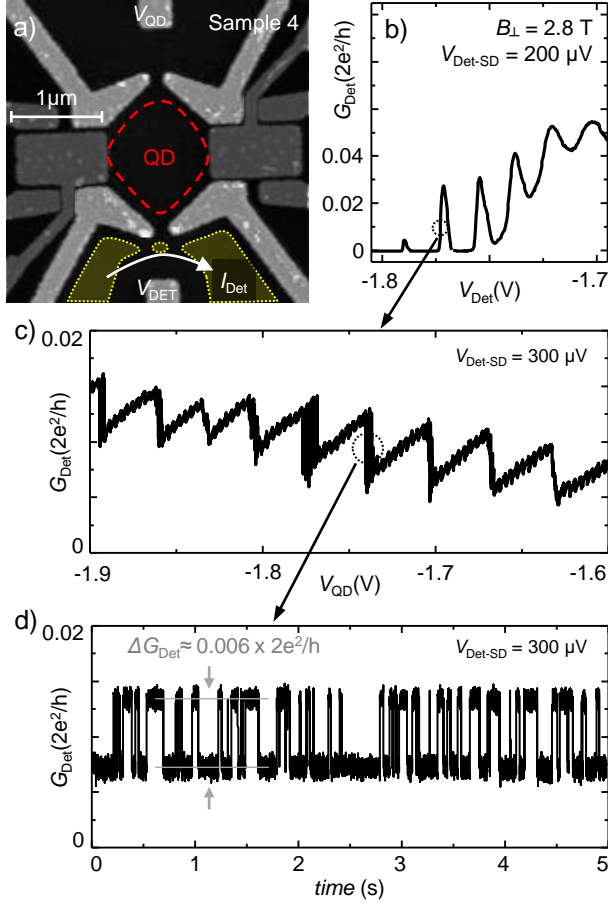

**Figure 5.** (color online) a) Atomic force micrograph of Sample 4. Four gates define a QD (red), the detector channel (yellow) is tuned into the localized regime. b) Differential conductance of the detector-localization as a function of  $V_{\text{Det}}$ . The position marked by a dashed circle is used for charge detection. c)  $G_{\text{Det}}$ , plotted as a function of  $V_{\text{QD}}$ . Big steps correspond to a change of the QD occupation by one electron. Small wiggles are caused by the simultaneous sweep of  $V_{\text{Det}}$  in order to keep the detector on the steep side of the localization's resonance. At the transition marked by a dashed circle,  $G_{\text{Det}}$  is measured with 1 kHz bandwidth as a function of time, as shown in d): A telegraph signal is created by electrons tunneling through the QD. The occupation numbers are separated by  $\Delta G_{\text{Det}} \sim 0.006 \times 2e^2/h$ .

After tuning the detector into the localized regime, Coulomb blockade oscillations of the detector are observed as a function of  $V_{\text{Det}}$ , as shown in figure 5b). Compared to Sample 3, the increased lateral size of the structure decreases the capacitance between QD and gates and hence decreases the spacing between charging events. The steepest slope (dashed circle) is used for charge detection of the QD. Figure 5c) shows the detector conductance as a function of  $V_{\text{QD}}$ , while  $V_{\text{Det}}$  is swept as a compensation to keep the detector at the flank of its Coulomb resonance. Periodic small wiggles are due to the finite resolution of the compensating voltage source, whereas large steps are caused by charging events of the QD. The tunnel rates of the QD are slow enough to observe them in real time, giving rise to telegraph noise at the border between adjacent occupation

numbers. At one of these borders (dashed circle), the detector current is recorded with 1 kHz bandwidth as a function of time and plotted in figure 5d). Clear two-level behavior separated by  $\Delta G_{\text{Det}} \sim 0.006 \times 2e^2/h$  is observed, demonstrating the high sensitivity of localized charge detectors. As a comparison, measuring the charge state with a QPC-like detector (data not shown) we observe conductance level separations of  $\Delta G_{\text{Det}} \sim 0.002 \times 2e^2/h$ . In future studies, we hope to extend the charge detection experiments to the regime of fractional quantum Hall states and to investigate time-dependent processes of such systems.

### 3. Conclusion

We investigated several methods of improving the sensitivity of charge detectors. The capacitive coupling between QD and detector was increased by using a floating gate. However, the increased sensitivity comes at the cost of charge rearrangements, making this technique difficult to handle in a typical gate-defined nanostructure. Introducing a gap in the barrier gates between QD and detector, we find a strongly enhanced sensitivity which is attributed to reduced screening, reduced lateral distance between QD and detector and a steeper detector slope due to the formation of a localized state. Formation and lateral shifting of the localized state was investigated and demonstrates that the detector can be tuned gradually from QPC-like to QD-like characteristics. Finally, the technique of using a localization for sensitive charge-readout was applied to a large QD in the quantum Hall regime.

### 4. Acknowledgments

We acknowledge the support of the ETH FIRST laboratory and financial support of the Swiss Science Foundation (Schweizerischer Nationalfonds, NCCR Quantum Science and Technology).

### References

- [1] Tsui D C, Stormer H L and Gossard A C 1982 *Physical Review Letters* **48** 1559–1562 URL <http://link.aps.org/doi/10.1103/PhysRevLett.48.1559>
- [2] Jain J K 1989 *Physical Review Letters* **63** 199–202 URL <http://link.aps.org/doi/10.1103/PhysRevLett.63.199>
- [3] Willett R, Eisenstein J P, Störmer H L, Tsui D C, Gossard A C and English J H 1987 *Physical Review Letters* **59** 1776–1779 URL <http://link.aps.org/doi/10.1103/PhysRevLett.59.1776>
- [4] Thomas K J, Nicholls J T, Simmons M Y, Pepper M, Mace D R and Ritchie D A 1996 *Physical Review Letters* **77** 135–138 URL <http://link.aps.org/doi/10.1103/PhysRevLett.77.135>
- [5] Kristensen A, Bruus H, Hansen A E, Jensen J B, Lindelof P E, Marckmann C J, Nygård J, Sørensen C B, Beuscher F, Forchel A and Michel M 2000 *Physical Review B* **62** 10950–10957 URL <http://link.aps.org/doi/10.1103/PhysRevB.62.10950>

- [6] Cronenwett S M, Lynch H J, Goldhaber-Gordon D, Kouwenhoven L P, Marcus C M, Hirose K, Wingreen N S and Umansky V 2002 *Physical Review Letters* **88** 226805 URL <http://link.aps.org/doi/10.1103/PhysRevLett.88.226805>
- [7] Goldhaber-Gordon D, Shtrikman H, Mahalu D, Abusch-Magder D, Meirav U and Kastner M A 1998 *Nature* **391** 156–159 ISSN 0028-0836 URL <http://www.nature.com/nature/journal/v391/n6663/full/391156a0.html>
- [8] Kouwenhoven L P and Glazman L 2001 *Physics World* **14** 33–38
- [9] Miller J B, Radu I P, Zumbühl D M, Levenson-Falk E M, Kastner M A, Marcus C M, Pfeiffer L N and West K W 2007 *Nature Physics* **3** 561–565 ISSN 1745-2473 URL <http://www.nature.com/nphys/journal/v3/n8/abs/nphys658.html>
- [10] Dolev M, Heiblum M, Umansky V, Stern A and Mahalu D 2008 *Nature* **452** 829–834 ISSN 0028-0836 URL <http://www.nature.com/nature/journal/v452/n7189/full/nature06855.html>
- [11] Zhang Y, McClure D T, Levenson-Falk E M, Marcus C M, Pfeiffer L N and West K W 2009 *Physical Review B* **79** 241304 URL <http://link.aps.org/doi/10.1103/PhysRevB.79.241304>
- [12] Ofek N, Bid A, Heiblum M, Stern A, Umansky V and Mahalu D 2010 *Proceedings of the National Academy of Sciences* ISSN 0027-8424, 1091-6490 URL <http://www.pnas.org/content/early/2010/03/02/0912624107>
- [13] Hayashi T, Fujisawa T, Cheong H D, Jeong Y H and Hirayama Y 2003 *Physical Review Letters* **91** 226804 URL <http://link.aps.org/doi/10.1103/PhysRevLett.91.226804>
- [14] Petta J R, Johnson A C, Taylor J M, Laird E A, Yacoby A, Lukin M D, Marcus C M, Hanson M P and Gossard A C 2005 *Science* **309** 2180–2184 ISSN 0036-8075, 1095-9203 URL <http://www.sciencemag.org/content/309/5744/2180>
- [15] Gustavsson S, Leturcq R, Simović B, Schleser R, Ihn T, Studerus P, Ensslin K, Driscoll D C and Gossard A C 2006 *Physical Review Letters* **96** 076605 URL <http://link.aps.org/doi/10.1103/PhysRevLett.96.076605>
- [16] Shinkai G, Hayashi T, Ota T and Fujisawa T 2009 *Physical Review Letters* **103** 056802 URL <http://link.aps.org/doi/10.1103/PhysRevLett.103.056802>
- [17] Frey T, Leek P J, Beck M, Blais A, Ihn T, Ensslin K and Wallraff A 2012 *Physical Review Letters* **108** 046807 URL <http://link.aps.org/doi/10.1103/PhysRevLett.108.046807>
- [18] Field M, Smith C G, Pepper M, Ritchie D A, Frost J E F, Jones G A C and Hasko D G 1993 *Physical Review Letters* **70** 1311–1314 URL <http://link.aps.org/doi/10.1103/PhysRevLett.70.1311>
- [19] Elzerman J M, Hanson R, Greidanus J S, Willems van Beveren L H, De Franceschi S, Vandersypen L M K, Tarucha S and Kouwenhoven L P 2003 *Physical Review B* **67** 161308 URL <http://link.aps.org/doi/10.1103/PhysRevB.67.161308>
- [20] Vandersypen L M K, Elzerman J M, Schouten R N, Willems van Beveren L H, Hanson R and Kouwenhoven L P 2004 *Applied Physics Letters* **85** 4394–4396 ISSN 00036951 URL [http://apl.aip.org/resource/1/applab/v85/i19/p4394\\_s1](http://apl.aip.org/resource/1/applab/v85/i19/p4394_s1)
- [21] Zhang L X, Leburton J P, Hanson R and Kouwenhoven L P 2004 *Applied Physics Letters* **85** 2628–2630 ISSN 00036951 URL [http://apl.aip.org/resource/1/applab/v85/i13/p2628\\_s1](http://apl.aip.org/resource/1/applab/v85/i13/p2628_s1)
- [22] Lu W, Ji Z, Pfeiffer L, West K W and Rimberg A J 2003 *Nature* **423** 422–425 ISSN 0028-0836 URL <http://www.nature.com/nature/journal/v423/n6938/full/nature01642.html>
- [23] Ilani S, Martin J, Teitelbaum E, Smet J H, Mahalu D, Umansky V and Yacoby A 2004 *Nature* **427** 328–332 ISSN 0028-0836 URL <http://www.nature.com/nature/journal/v427/n6972/abs/nature02230.html>
- [24] Martin J, Ilani S, Verdene B, Smet J, Umansky V, Mahalu D, Schuh D, Abstreiter G and Yacoby A 2004 *Science* **305** 980–983 ISSN 0036-8075, 1095-9203 URL <http://www.sciencemag.org/content/305/5686/980>
- [25] Barthel C, Kjærgaard M, Medford J, Stopa M, Marcus C M, Hanson M P and Gossard A C 2010 *Physical Review B* **81** 161308 URL <http://link.aps.org/doi/10.1103/PhysRevB.81.161308>
- [26] Shorubalko I, Leturcq R, Pfund A, Tyndall D, Krtschek R, Schon S and Ensslin K 2008 *Nano Lett.*

- 8 382–385 ISSN 1530-6984 URL <http://dx.doi.org/10.1021/nl072522j>
- [27] Choi T, Shorubalko I, Gustavsson S, Schön S and Ensslin K 2009 *New Journal of Physics* **11** 013005 ISSN 1367-2630 URL <http://iopscience.iop.org/1367-2630/11/1/013005>
  - [28] Rössler C, Küng B, Dröscher S, Choi T, Ihn T, Ensslin K and Beck M 2010 *Applied Physics Letters* **97** 152109–152109–3 ISSN 00036951 URL [http://apl.aip.org/resource/1/applab/v97/i15/p152109\\_s1](http://apl.aip.org/resource/1/applab/v97/i15/p152109_s1)
  - [29] Friedland K J, Hey R, Kostial H, Klann R and Ploog K 1996 *Physical Review Letters* **77** 4616–4619 URL <http://link.aps.org/doi/10.1103/PhysRevLett.77.4616>
  - [30] Umansky V, de Picciotto R and Heiblum M 1997 *Applied Physics Letters* **71** 683–685 ISSN 00036951 URL [http://apl.aip.org/resource/1/applab/v71/i5/p683\\_s1](http://apl.aip.org/resource/1/applab/v71/i5/p683_s1)
  - [31] Rössler C, Feil T, Mensch P, Ihn T, Ensslin K, Schuh D and Wegscheider W 2010 *New Journal of Physics* **12** 043007 ISSN 1367-2630 URL <http://iopscience.iop.org/1367-2630/12/4/043007>
  - [32] Rössler C, Baer S, de Wiljes E, Ardelt P L, Ihn T, Ensslin K, Reichl C and Wegscheider W 2011 *New Journal of Physics* **13** 113006 ISSN 1367-2630 URL <http://iopscience.iop.org/1367-2630/13/11/113006>
  - [33] Gamez G and Muraki K 2011 *arXiv:1101.5856* URL <http://arxiv.org/abs/1101.5856>
  - [34] Gustavsson S, Studer M, Leturcq R, Ihn T, Ensslin K, Driscoll D C and Gossard A C 2007 *Physical Review Letters* **99** 206804 URL <http://link.aps.org/doi/10.1103/PhysRevLett.99.206804>
  - [35] Taubert D, Pioro-Ladrière M, Schröer D, Harbusch D, Sachrajda A S and Ludwig S 2008 *Physical Review Letters* **100** 176805 URL <http://link.aps.org/doi/10.1103/PhysRevLett.100.176805>
  - [36] Gasser U, Gustavsson S, Küng B, Ensslin K, Ihn T, Driscoll D C and Gossard A C 2009 *Physical Review B* **79** 035303 URL <http://link.aps.org/doi/10.1103/PhysRevB.79.035303>
  - [37] Küng B, Gustavsson S, Choi T, Shorubalko I, Ihn T, Schön S, Hassler F, Blatter G and Ensslin K 2009 *Physical Review B* **80** 115315 URL <http://link.aps.org/doi/10.1103/PhysRevB.80.115315>
  - [38] Vink I T, Nooitgedagt T, Schouten R N, Vandersypen L M K and Wegscheider W 2007 *Applied Physics Letters* **91** 123512–123512–3 ISSN 00036951 URL [http://apl.aip.org/resource/1/applab/v91/i12/p123512\\_s1](http://apl.aip.org/resource/1/applab/v91/i12/p123512_s1)
  - [39] Müller T 2011 *Radio-Frequency Quantum Point Contact Charge Detection* Ph.D. thesis ETH Zürich Zürich
  - [40] Chan I, Fallahi P, Westervelt R, Maranowski K and Gossard A 2003 *Physica E: Low-dimensional Systems and Nanostructures* **17** 584–588 ISSN 1386-9477 URL <http://www.sciencedirect.com/science/article/pii/S1386947702008767>
  - [41] Hübel A, Weis J, Dietsche W and Klitzing K v 2007 *Applied Physics Letters* **91** 102101–102101–3 ISSN 00036951 URL [http://apl.aip.org/resource/1/applab/v91/i10/p102101\\_s1](http://apl.aip.org/resource/1/applab/v91/i10/p102101_s1)
  - [42] Churchill H O H, Bestwick A J, Harlow J W, Kuemmeth F, Marcos D, Stwertka C H, Watson S K and Marcus C M 2009 *Nature Physics* **5** 321–326 ISSN 1745-2473 URL <http://www.nature.com/nphys/journal/v5/n5/full/nphys1247.html>
  - [43] Büttiker M 1990 *Physical Review B* **41** 7906–7909 URL <http://link.aps.org/doi/10.1103/PhysRevB.41.7906>
  - [44] Schnez S, Rössler C, Ihn T, Ensslin K, Reichl C and Wegscheider W 2011 *Physical Review B* **84** 195322 URL <http://link.aps.org/doi/10.1103/PhysRevB.84.195322>
  - [45] McEuen P, Alphenaar B, Wheeler R and Sacks R 1990 *Surface Science* **229** 312–315 ISSN 0039-6028 URL <http://www.sciencedirect.com/science/article/pii/003960289090896G>
  - [46] Meir Y, Hirose K and Wingreen N S 2002 *Physical Review Letters* **89** 196802 URL <http://link.aps.org/doi/10.1103/PhysRevLett.89.196802>
  - [47] Reilly D J 2005 *Physical Review B* **72** 033309 URL <http://link.aps.org/doi/10.1103/PhysRevB.72.033309>
  - [48] Güttinger J, Stampfer C, Hellmüller S, Molitor F, Ihn T and Ensslin K 2008 *Applied Physics*

*Letters* **93** 212102–212102–3 ISSN 00036951 URL [http://apl.aip.org/resource/1/applab/v93/i21/p212102\\_s1](http://apl.aip.org/resource/1/applab/v93/i21/p212102_s1)